

Process Guidelines

MEGTRON4

Laminate R-5725

Prepreg R-5620

High Speed, Low Loss Multi-layer Materials

General

Material Storage

R-5725 laminate and R-5620 prepreg is the same as our conventional FR-4 material.

Laminate should be stored flat in a cool dry environment. Avoid bending or scratching the laminate surface.

When possible store the laminate in the original container.

Prepreg should be stored flat in a cool dry controlled environment, 73 F(23 C) or less and 50% RH or less.

Laminate Surface Preparation

Regular Shiny Copper can be cleaned using industry standard chemical clean or mechanical clean.

Reverse Treat Copper should be cleaned using industry standard chemical clean.

Inner Layer Bond Treatment

Black or Brown Oxide can be used.

Alternative Oxide Treatment using a Peroxide/Sulfuric etch technology can be also used.

Drying

Dry finished inner layers completely to remove any absorbed moisture or surface moisture. A racked bake at 300 F(150 C) for 1-2 hours is preferred. For conveyORIZED alternative oxide processing, some equipment may have sufficient drying capability. However, a racked bake is suggested.



Drilling (1) Drilling parameters in general condition

Drilling parameters should be adjusted depending on hole size, layer count, panel thickness, stack count and stack height etc.

(1) Drilling parameters in general condition

diameter	spindle	velocity	min		max		bit life
			infeed	chipload	infeed	chipload	
mm	rpm	m/min	m/min	μ /rev	m/min	μ /rev	hits
0.20	160,000	100	1.6	10	2.4	15	750-2,000
0.25	160,000	126	1.8	11	2.8	18	750-2,000
0.30	160,000	151	1.9	12	3.2	20	1,500-3,000
0.35	137,000	151	1.8	13	3.0	22	1,500-3,000
0.40	120,000	151	1.8	15	2.9	24	1,500-3,000
0.45	107,000	151	1.8	17	2.7	25	1,500-3,000
0.50	96,000	151	1.8	19	2.7	28	1,500-3,000
0.55	87,000	150	1.8	21	2.6	30	1,500-3,000
0.60	80,000	151	1.7	21	2.6	33	1,500-3,000
0.65	74,000	151	1.7	23	2.6	35	1,500-3,000
0.70	68,000	149	1.7	25	2.6	38	1,500-3,000
0.75	64,000	151	1.6	25	2.6	41	1,500-3,000
0.80	60,000	151	1.6	27	2.5	42	1,500-3,000
0.85	56,000	149	1.6	29	2.4	43	1,500-3,000
0.90	53,000	150	1.6	30	2.4	45	1,500-3,000




The following guidelines are provided as general recommendations. Process optimization may be necessary.

Drilling (2) Positioning accuracy


(2) Positioning accuracy

Drill size	mm	0.3
Surface speed	m/min	151
Revolution	rpm	160000
Chip load	micron/rev	20
Hit count		3000
Entry board		0.15 Aluminum (lubricated is preferred)
Panel thickness	mm	0.8 (#7628 X 4)
Copper thickness	micron	35 / 35
Stack count		4

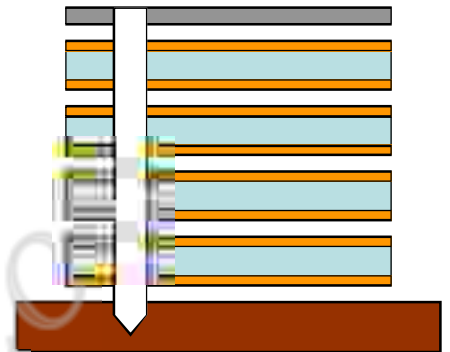


Positioning accuracy map of R-5725 and R-1766 as our conventional FR-4

R-5725

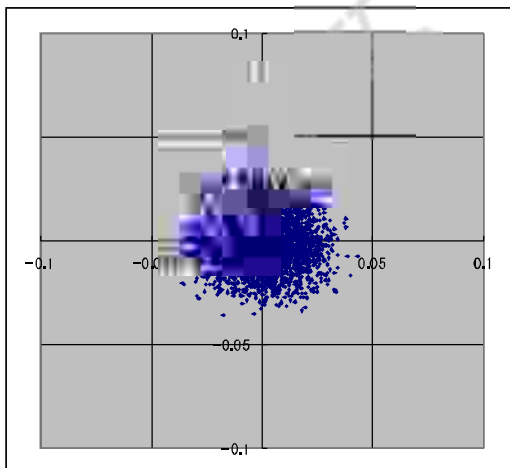

positioning accuracy : 46.6 micron

R-1766

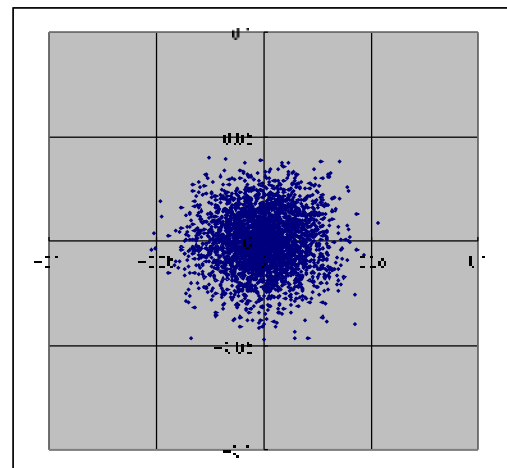

positioning accuracy : 47.2 micron




The following guidelines are provided as general recommendations.
Process optimization may be necessary.

Laminate

Curing temperature time will be determined by the thickness of multilayer package being laminated.

Laminate parameters should be adjusted depending on board thickness, stack count and stack thickness etc.

Please Note : below is NOT a press control program. The graph represents the recommended pressure/temperature profile that the actual panels are subjected to during the lamination program cycle.

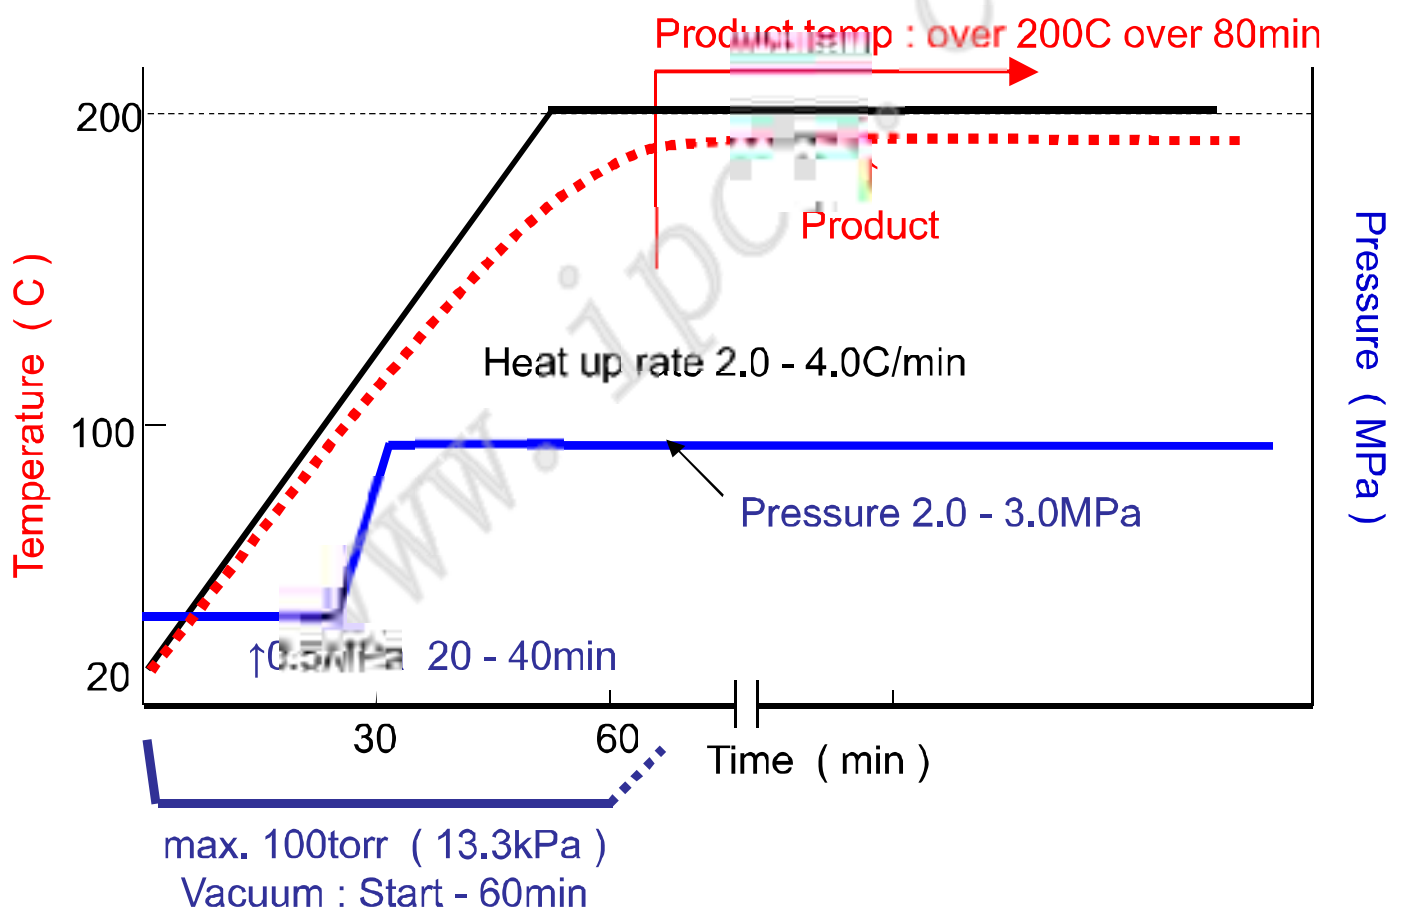

The following guidelines are provided as general recommendations. Process optimization may be necessary.

Desmear

The weight loss of R-5725 laminate and R-5620 prepreg is less than that of R-1766 as our conventional FR-4 material.

Desmear parameters should be adjusted depending on board thickness, stack count and stack thickness etc.

process	reagent type	temp. (C)	time (min)
Swelling	alkaline	65-85	5-10
Etching	permanganate	70-85	10-15

process	reagent type	temp. (C)	time (min)
Swelling	organic solvent	35-40	6-10
Etching	permanganate	70-85	10-15

Part number	Weight loss ratio
R-5725	0.3 - 0.7
R-1766	1.0



The following guidelines are provided as general recommendations. Process optimization may be necessary.

++Before purchase++**【Notes before you use】**

- Prior to adoption and use of a product contained in the Process Guideline, please verify the suitability for your application by your quality testing, evaluation, etc.
- We would like to have a delivery specifications mutually agreed for the product that you have decided to use.
The agreements defined in the delivery specifications are assigned higher priority.
- Please note that images shown may somewhat differ from the actual product in color.
- Please note that specifications and external design are subject to change for product improvement without notice.
- For details on products in the Process Guideline, please contact your distributor or our sales department.

【Safety Information】

- Before using the product, please read the delivery specifications carefully or contact the distributor from which you purchased the product or our sales department in order to use the product correctly.
- The products in the Process Guideline are **Electronic circuit board materials** for electronic and electrical devices. **Please do not use them for other than specified use.**